

Small Angle Neutron Scattering as a New Tool to Evaluate Moisture-Induced Swelling in the Nanostructure of Chemically Modified Wood Cell Walls

Nayomi Z. Plaza*, Joseph E. Jakes, Charles R. Frihart, Christopher G. Hunt, Daniel J. Yelle, & Linda F. Lorenz, *Forest Biopolymers Science and Engineering, USDA Forest Service, Forest Products Laboratory, Madison, WI, USA*; William T. Heller & Sai Venkatesh Pingali, *Biology and Soft Matter Division, Oak Ridge National Laboratory, Oak Ridge, TN, USA*; Donald S. Stone, *Department of Materials Science and Engineering, University of Wisconsin-Madison, Madison, WI, USA*.

*e-mail: nayomiplazarodriguez@fs.fed.us

ABSTRACT

Wood-based products can be a sustainable and more environmentally friendly alternative to traditional construction materials because of their reduced contribution to air and water pollution. An integral component of these products is often an adhesive. Because wood is hygroscopic, moisture-induced swelling in the cell walls near the wood–adhesive bondlines can lead to durability and performance issues. Unfortunately, researchers working towards improving the moisture durability of forest products are hindered by an incomplete understanding of the nanoscale mechanisms that contribute to moisture-induced swelling in wood and how chemical modifications affect the swelling. Therefore, we developed small angle neutron scattering (SANS) into a tool that can study the 1-100 nm structure of unmodified and chemically modified wood cell walls and can measure the effects of moisture in this structure. In this study, SANS was used to reveal the nanostructure of a deuterium-labelled phenol formaldehyde (dPF) adhesive infiltrated into wood cell walls. The results revealed that the dPF infiltrated the water-accessible regions between the elementary fibrils inside the wood cell walls. These results provide the new insight that adhesive infiltration into the cellulose microfibril (a bundle of elementary fibrils) may be a key to designing moisture-durable wood adhesives.

INTRODUCTION

Most wood-based construction materials, including plywood, particle board, oriented strandboard, and structural wood products, are made of wood components held together by an adhesive. Phenol-formaldehyde (PF) is one of the most moisture-durable wood adhesives, and its durability is thought to originate from its ability to modify the properties of cell walls near the wood–adhesive bondline (Frihart 2009). However, because PF was empirically developed over decades, the mechanisms behind its durability are not well understood. For instance, although it is known that PF with low molecular weight can infiltrate the cell wall, its nanoscale interactions with the wood cell ultrastructure are still an active area of research (Laborie and Frazier 2006, Laborie et al. 2006, Jakes et al. 2015). It is widely debated if PF is chemically bonded with the lignocellulosic polymers, although recent studies using solution-state nuclear magnetic resonance (NMR) have proposed that two competing processes might occur while PF cures inside the cell wall: lignin degradation and formation of methylene bridges between lignin and PF (Yelle and Ralph 2016a, 2016b). The nanostructure of PF-infiltrated cell walls is not known.

Small angle neutron scattering (SANS) is a powerful technique capable of probing the nanostructure of organic materials like adhesives and wood cell walls. Neutrons are uncharged elementary particles that interact with organic materials via neutron–nuclei interactions. In SANS, a beam of neutrons is focused on a sample and the neutrons that are scattered at small scattering angles are detected on a two-dimensional (2D) detector. The scattered intensity provides information about the size, shape, and orientation of the sample nanostructure. One of the main advantages of neutron scattering is its isotope sensitivity, which allows enhancement of the scattering from nanostructures by selective deuterium labelling (Langan et al. 2012). Moreover, solutions of H₂O and D₂O can be used to contrast match certain nanoscale features and remove their scattering contributions (Hammouda 2010).

SANS has become an increasingly popular tool in lignocellulosic research, particularly to study the pretreatment effects on the nanostructure of isolated wood cell wall polymers (Pingali et al. 2010b, Petridis et al. 2011) as well as native wood cell walls (Nishiyama et al. 2014, Ding and Himmel 2006, Pingali et al. 2010a). SANS also has been found capable of measuring the spacing between elementary fibrils in wood cell walls as a function of moisture content (Fernandes et al. 2011, Plaza et al. 2016). Plaza (2017) and Plaza and others (2016) recently used the increase in spacing between elementary fibrils measured with SANS to show that more than half of the swelling in

the transverse plane of the S2 cell wall layer was caused by swelling between elementary fibrils. This finding is in direct contrast to previous research that attributed the majority of the swelling in the S2 layer to swelling of the lignin–hemicellulosic matrix within the S2 layer (Boutelje 1962, Rafsanjani et al. 2014).

The key to minimizing swelling in the wood cell wall is to minimize the swelling between elementary fibrils. Based on this insight, we decided to use SANS to investigate if the known moisture-durable PF adhesive modifies the microfibrils, which are bundles of elementary fibrils. The SANS results undoubtedly showed that PF can infiltrate between the elementary fibrils. This new understanding that adhesives can infiltrate and modify the microfibrils in wood cell walls provides new information for researchers developing and improving moisture-durable wood adhesives.

MATERIALS AND METHODS

Tangential–longitudinal latewood samples of loblolly pine (*Pinus taeda*) were cut to 25 by 25 by 0.5 mm from a single growth ring. An unmodified control sample was kept as cut. The sample to be infiltrated was vacuum-dried for 30 min to remove moisture before adhesive infiltration. Low-molecular-weight dPF was synthesized according to Laborie’s methods (Laborie 2002). To synthesize the resin, perdeuterated phenol crystals were mixed with 20% perdeuterated formaldehyde solution in D₂O and sodium deuterioxide solution in P/F/NaOD molar ratios of 1:2:0.2. Then, the reaction flask was immersed in an oil bath and heated at 80°C for 40 min. The vacuum-dried samples were immersed in the dPF resin, vacuum-treated at room temperature for 30 min to infiltrate the samples, and soaked for 24 h using glass stoppers to keep the wood samples submerged. The samples were removed from the resin, and the excess dPF was wiped off. Residual dPF was removed from the lumina by vacuum-treating the samples for 30 min. Then, the samples were heat-treated at 155 to 160°C for 30 min in an oven to cure the dPF. A total weight gain of 29% was measured for the sample infiltrated with dPF.

SANS experiments were performed with the EQ-SANS instrument (Zhao et al. 2010) at the Spallation Neutron Source at the Oak Ridge National Laboratory (Oak Ridge, Tennessee, USA). Data were acquired using a sample-to-detector distance of 1.3 m and a minimum wavelength of 2.5 Å. The beam was collimated with aperture diameters of 25 and 12 mm for the source and sample, respectively. Data were recorded using a 2D (1 x 1 m²) ³He linear position-sensitive detector with 192 x 256 pixels. Scattering patterns were normalized to the incident beam and monitor counts; corrected for time of flight, pixel sensitivity, dark current, and background contributions; and scaled to absolute units using MantidPlot (Arnold et al. 2014).

The samples were placed in square quartz holders, which were sealed with Kapton (Dupont, USA) tape. The 0.5-mm cavity inside the holders was filled with D₂O or a 35:65 D₂O/H₂O solution using a syringe. All air bubbles were removed before the samples were placed in the translation stage at the beamline. The 35:65 D₂O/H₂O solution, for which scattering length density (SLD) corresponded to the cellulose contrast matching point (CCMP), was used to remove the scattering contributions from the wood polymers. Unmodified wood was measured in both pure D₂O and the CCMP solution. The dPF-infiltrated wood was only measured in the CCMP solution to enhance scattering from the dPF. Samples were soaked overnight in D₂O or the CCMP solution before being placed in the holders.

RESULTS AND DISCUSSION

The 2D scattering patterns from unmodified wood immersed in pure D₂O, unmodified wood immersed in the CCMP solution, and dPF-infiltrated wood in the CCMP solution are shown in Figure 1a-c, respectively. Schematics of the transverse cross section of the microfibrils giving rise to the 2D scattering patterns from unmodified wood in pure D₂O, unmodified wood in the CCMP solution, and dPF-infiltrated wood in the CCMP solution are shown in Figure 1d-e, respectively.

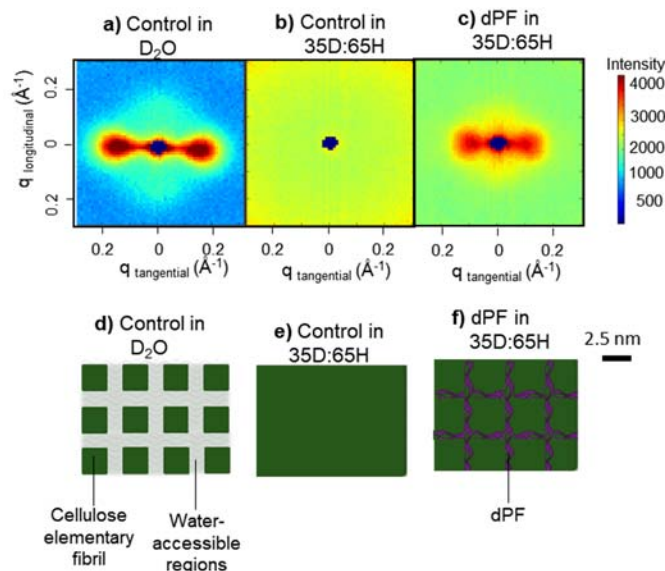


Figure 1: Small angle neutron scattering (SANS) patterns from unmodified wood in (a) pure D₂O and (b) CCMP solution. SANS patterns from (c) dPF-infiltrated wood in the CCMP solution. Schematics of the scattering length density distribution at the microfibril level that gives rise to the SANS patterns from unmodified wood in (d) pure D₂O and (e) CCMP solution and dPF-infiltrated wood in (f) CCMP solution. A transverse view of the microfibril is shown for simplicity although SANS patterns were obtained from tangential–longitudinal samples.

In the scattering pattern from the unmodified wood in pure D₂O, lobes along the equatorial axis were observed. These lobes correspond to fiber diffraction peaks that arise from the regular spacing between the elementary fibrils (Fernandes et al. 2011, Plaza et al. 2016). The scattering contrast is provided by the difference in SLDs between the water-inaccessible elementary fibrils and the D₂O (1.9×10^{10} vs. $6.4 \times 10^{10} \text{ cm}^{-2}$) that entered the water-accessible regions between elementary fibrils (Fig. 1d). As expected, the pattern from unmodified wood in the CCMP solution (Fig. 1b) did not have lobes because of the lack of contrast between the cellulose elementary fibrils and the CCMP solution (Fig. 1e). However, lobes were observed in the pattern from the dPF-infiltrated wood in the CCMP solution (Fig. 1c). The only explanation for these lobes is that the dPF, for which SLD was comparable with D₂O, was occupying the regularly spaced regions between the elementary fibrils (Fig. 1f).

The SANS results in Figure 1 unambiguously show that a PF adhesive not only infiltrates the wood cell wall but can also infiltrate the cellulose microfibril. More research is needed to fully understand how the microfibril infiltration is related to moisture-induced swelling at larger length scales and the moisture durability of wood–adhesive bondlines. Nevertheless, in this report, we demonstrated the power of SANS to study the nanoscale interactions between adhesives and wood ultrastructure. In the future, we can also use our in situ humidity chamber (Plaza et al. 2016) to measure the effects of PF infiltration on the elementary fibril swelling as a function of humidity.

CONCLUSIONS

Using SANS, we discovered that the moisture-durable wood adhesive PF can infiltrate cellulose microfibrils in wood cell walls. This discovery suggests that to make a moisture-durable bond, infiltrating and modifying the cellulose microfibril is necessary to limit the moisture-induced swelling in the microfibrils. SANS is also a uniquely suited tool to study these types of nanoscale interactions between the adhesive and wood cell wall ultrastructure. In the future, similar SANS work could be performed to further our understanding of how to make moisture-durable wood adhesives by studying different bonding factors such as type of adhesive, adhesive molecular weight, and different infiltration conditions. These results should accelerate the development of new and improved wood adhesives.

ACKNOWLEDGEMENTS

NP acknowledges the GERS program at UW–Madison, 2012 NSF GFRP, US Forest Service Pathways program, and 2016 DOE SCGSR for support. JEJ acknowledges funding from 2011 USDA PECASE awards. JEJ and NP acknowledge support from the FHA Cooperative Research Program for Covered Timber Bridges. The use of Spallation Neutron Source facilities was supported by the Scientific User Facilities Division, Office of Basic Energy Sciences, U.S. Department of Energy. SVP acknowledges the Genomic Science Program, Office of Biological and Environmental Research, U.S. Department of Energy (FWP ERKP752).

REFERENCES

- Arnold O., Bilheux J. C., Borreguero J. M., Buts A., Campbell S. I., Chapon L., Doucet M., et al. 2014. Mantid - Data analysis and visualization package for neutron scattering and μ SR experiments. *Nuclear Instruments and Methods in Physics Research, Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*, 764: 156–166. doi:10.1016/j.nima.2014.07.029.
- Boutelje J. B. 1962. The relationship of structure to transverse anisotropy in wood with reference to shrinkage and elasticity. *Holzforschung*, 16, 2: 33–46. doi:10.1515/hfsg.1962.16.2.33.
- Ding S.-Y., Himmel M. E. 2006. The maize primary cell wall microfibril: A new model derived from direct visualization. *Journal of Agricultural and Food Chemistry*, 54, 3: 597–606. doi:10.1021/jf051851z.
- Fernandes A. N., Thomas L. H., Altaner C. M., Callow P., Forsyth V. T., Apperley D. C., Kennedy C. J., Jarvis M. C. 2011. Nanostructure of cellulose microfibrils in spruce wood. *Proceedings of the National Academy of Sciences of the United States of America*, 108, 47: 1195–1203. doi:10.1073/pnas.1108942108.
- Frihart C. R. 2009. Adhesive groups and how they relate to the durability of bonded wood. *Journal of Adhesion Science and Technology*, 23, 4: Netherlands: VSP BV: 611–627. doi:10.1163/156856108X379137.
- Hammouda B. 2010. Probing nanoscale structures—the sans toolbox. *NIST Center for Neutron Research*, 224. doi:10.1016/j.nano.2007.10.035.
- Jakes J. E., Hunt C. G., Yelle D. J., Lorenz L., Hirth K., Gleber S. C., Vogt S., Grigsby W., Frihart C. R. 2015. Synchrotron-based x-ray fluorescence microscopy in conjunction with nanoindentation to study molecular-scale interactions of phenol formaldehyde in wood cell walls. *ACS Applied Materials & Interfaces*, 7, 12: 6584–6589. doi:10.1021/am5087598.
- Laborie M.-P. G. 2002. Investigation of the wood/ phenol-formaldehyde adhesive interphase morphology. PhD Dissertation. Blacksburg, Virginia, Virginia Polytechnic Institute and State University.
- Laborie, M.-P. G., Salmén L., Frazier C. E. 2006. A morphological study of the wood/phenol-formaldehyde adhesive interphase. *Journal of Adhesion Science and Technology*, 20, 8: 729–741. doi:10.1163/15685610677638743.
- Laborie M.-P. G., Frazier C. E. 2006. ¹³C CP/MAS NMR study of a wood/phenol-formaldehyde resin bondline. *Journal of Materials Science*, 41, 18: 6001–6005. doi:10.1007/s10853-006-0497-6.
- Langan P., Evans B. R., Foston M., Heller W. T., O'Neill H., Petridis L., Pingali S. V., et al. 2012. Neutron technologies for bioenergy research. *Industrial Biotechnology*, 8, 4: 209–216. doi:10.1089/ind.2012.0012.
- Nishiyama Y., Langan P., O'Neill H., Pingali S. V., Harton S. 2014. Structural coarsening of aspen wood by hydrothermal pretreatment monitored by small- and wide-angle scattering of x-rays and neutrons on oriented specimens. *Cellulose*, 21, 2: 1015–1024. doi:10.1007/s10570-013-0069-2.
- Petridis L., Pingali S., Urban V., Heller W., O'Neill H., Foston M., Ragauskas A., Smith J. 2011. Self-similar multiscale structure of lignin revealed by neutron scattering and molecular dynamics simulation. *Physical Review, E*, 83, 6: 4–7. doi:10.1103/PhysRevE.83.061911.
- Pingali S. V., Urban V. S., Heller W. T., McGaughey J., O'Neill H., Foston M., Myles D. A., Ragauskas A., Evans B. R. 2010a. Breakdown of cell wall nanostructure in dilute acid pretreated biomass. *Biomacromolecules*, 11, 9: 2329–2335. doi:10.1021/bm100455h.
- Pingali S. V., Volker S. U., Heller W. T., McGaughey J., O'Neill H. M., Foston M., Myles D. A., Ragauskas A. J., Evans B. R. 2010b. SANS study of cellulose extracted from switchgrass. *Acta Crystallographica Section D Biological Crystallography*, 66 (11). International Union of Crystallography: 1189–1193. doi:10.1107/S0907444910020408.
- Plaza N. Z. 2017. Neutron scattering studies of nano-scale wood-water interactions. Madison, Wisconsin, University of Wisconsin-Madison.
- Plaza N. Z., Pingali S. V., Qian S., Heller W. T., Jakes J. E. 2016. Informing the improvement of forest products durability using small angle neutron scattering. *Cellulose*, 23, 3. Springer Netherlands: 1593–1607.

doi:10.1007/s10570-016-0933-y.

Rafsanjani A., Stiefel M., Jefimovs K., Mokso R., Derome D., Carmeliet J. 2014. Hygroscopic swelling and shrinkage of latewood cell wall micropillars reveal ultrastructural anisotropy. *Journal of The Royal Society Interface*, 11, 95: 20140126–20140126. doi:10.1098/rsif.2014.0126.


Yelle D. J., Ralph J. 2016a. Characterizing phenol-formaldehyde adhesive cure chemistry within the wood cell wall. *International Journal of Adhesion and Adhesives*, 70. Elsevier: 26–36. doi:10.1016/j.ijadhadh.2016.05.002.

Yelle D. J., Ralph J. 2016b. Simultaneous bond degradation and bond formation during phenol-formaldehyde curing with wood. In *WCTE 2016 World Conference Timber Engineering*. Vienna, Austria.

Zhao J. K., Gao C. Y., Liu D. 2010. The extended Q-range small-angle neutron scattering diffractometer at the SNS. *Journal of Applied Crystallography*, 43, 5 PART 1: 1068–1077. doi:10.1107/S002188981002217X.



International Conference on **Wood Adhesives**

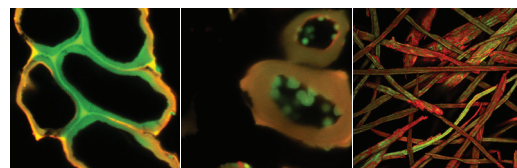

OCTOBER 25-27, 2017
Atlanta, Georgia, USA

Proceedings of the 2017 International Conference on Wood Adhesives, Oct 25-27, Atlanta, GA. USA. Christopher G. Hunt, Gregory D. Smith, Ning Yan, eds. Published by Forest Products Society, Peachtree Corners, GA 2017

Proceedings

FOREST
PRODUCTS
SOCIETY